




Wood Preservation Canada
Préservation du bois Canada






SPECIFIER GUIDE

No. WPC – 01-2025

Crossarms

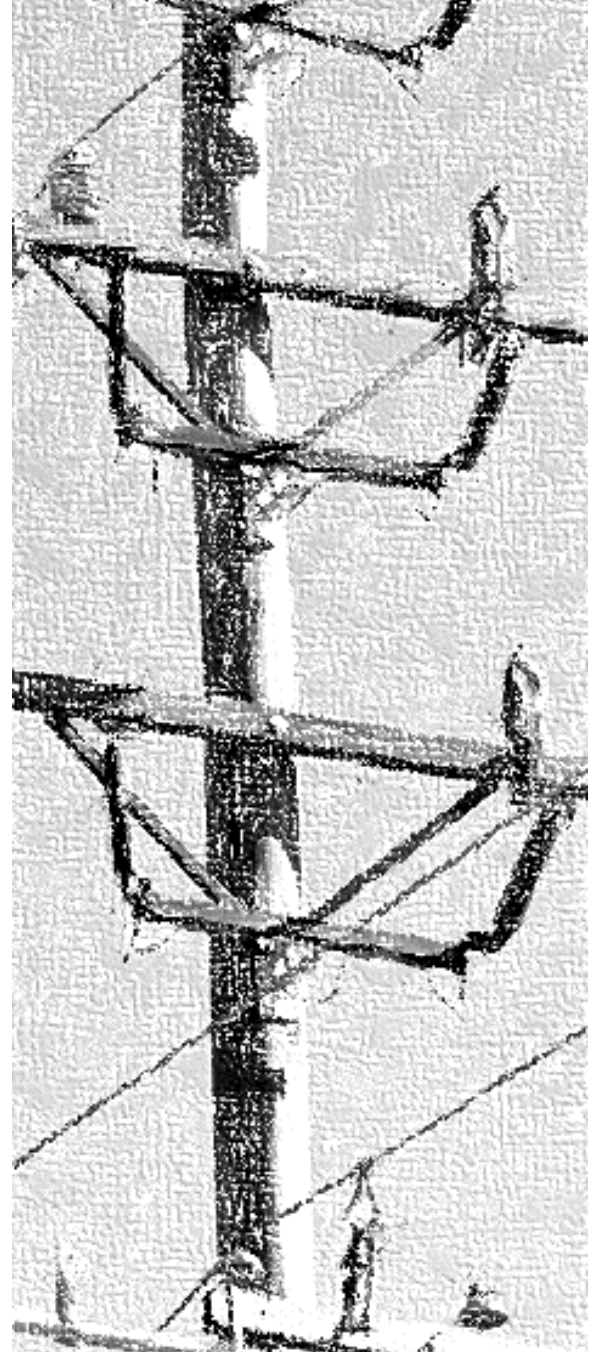

Wood Preservation Canada • 613-737-4337 • info@woodpreservation.ca Wood Preservation Canada provides this information from sources believed to be true. However, neither WPC or its members guarantee the accuracy of any information published herein and these parties are not responsible for any errors, omissions or damages arising out of or relating to its use. This document is published with the understanding that WPC, its members and the authors are supplying information, but are not attempting to render engineering or other professional services.



SPECIFYING CROSSARMS

WPC – 01-2025

Product Introduction

Pressure treated wood crossarms are beams that are typically square and mounted at right angles on a utility pole to secure the transmission wires and provide a transfer point that can carry multiple wires along the utility service corridor from pole to pole. Crossarms are typically manufactured based on specifications as provide by or indicated by the purchaser.

The information in this guide focuses only on the requirements for pressure treating of pressure treated sawn crossarms as specified in the CAN / CSA O80-21 Wood Preservation.






Allowable Wood Species and Related Use Categories

While pressure treated crossarms are not in ground contact they are subject to substantial vertical loads and their integrity coupled with long-term performance is an important quality required in utility lines. Under general service conditions crossarms have a Use Category rating of UC3.2 and where the conditions are deemed critical or hard to replace applications a Use Category rating of UC4.1. The processing and treatment of these products shall be done in accordance with CSA O80.2-21.

Preservative Systems Used in Treatment Crossarms – Sawn*		
Chemical Name	Abbreviation	Allowable Use Categories
Ammoniacal Copper Zinc Arsenate	ACZA	UC 3.2, UC4.1
Copper Azole Type B	CA-B	UC 3.2, UC4.1
Chromated Copper Arsenate	CCA	UC 3.2, UC4.1
Creosote	CR	UC 3.2, UC4.1
Copper Naphthenate	CuN	UC3.2, UC4.1
Pentachlorophenol	PCP-A or C	UC 3.2, UC4.1

**Refer to CAN / CSA O80.1-21 Table 11 for complete details.
Source - CAN/CSA-O80 Series-21, Wood preservation. © 2021 Canadian Standards Association*

Preservative Treatments – Crossarms – Sawn – UC3.2						
UC3.2 – General Applications - Above Ground – Exterior						
Species Group	Preservative System Retention – kg/m ³ *					
	ACZA	CA-B	CCA	CR	CuN	PCP-A & C
Jack pine	4.0	1.7	4.0	96		4.8
Lodgepole pine	4.0	1.7	4.0	96		4.8
Red pine	4.0	1.7	4.0	96		4.8
Southern pine	4.0	1.7	4.0	96	0.64	4.8
Western Hemlock	4.0	1.7	4.0	96		6.4
Coastal Douglas fir	4.0	1.7	4.0	96	0.64	6.4



SPECIFYING CROSSARMS

WPC – 01-2025

Interior Douglas fir	4.0	1.7	4.0	96	0.64	6.4
Western larch	4.0		4.0	96		4.8
Yellow cypress	4.0		4.0	96		4.8

**Refer to CAN / CSA O80.1-21 Table 10 for complete details*

Source - CAN/CSA-O80 Series-21 Wood preservation. © 2021 Canadian Standards Association

Preservative Treatments – Crossarms – Sawn – UC4.1

UC4.1 – Critical or Hard to Replace Applications - Exterior

Species Group	Preservative System Retention – kg/m ³ *					
	ACZA	CA-B	CCA	CR & CR-S	CuN	PCP-A & C
Jack pine	6.4	3.3	6.4	128		6.4
Lodgepole pine	6.4	3.3	6.4	128		6.4
Red pine	6.4	3.3	6.4	128		6.4
Southern pine	6.4	3.3	6.4	128	0.8	6.4
Western Hemlock	6.4	3.3	6.4	120		6.4
Coastal Douglas fir	6.4	3.3	6.4	120	0.8	6.4
Interior Douglas fir	6.4	3.3	6.4	120	0.8	6.4
Western larch	6.4		6.4	128		6.4
Yellow cypress	6.4		6.4	128		6.4

**Refer to CAN / CSA O80.1-21 Table 10 for complete details*

Source - CAN/CSA-O80 Series-21 Wood preservation. © 2015 Canadian Standards Association

Product registration

Wood Preservatives and their uses are regulated by Health Canada's Pest Management Regulatory Agency (PMRA).

Recommended Reference Standards

CAN / CSA O80 Series 21 - Wood Preservation®

Source © 2015 Canadian Standards Association

With the permission of Canadian Standards Association, (operating as "CSA Group"), 178 Rexdale Blvd., Toronto, ON, M9W 1R3, material is reproduced from CSA Group's standard **CAN/CSA-O80 Series 21 Series – Wood Preservation**. This material is not the complete and official position of CSA Group on the referenced subject, which is represented solely by the Standard in its entirety. While use of the material has been authorized, CSA Group is not responsible for the manner in which the data is presented, nor for any representations and interpretations. No further reproduction is permitted.

For more information or to purchase standard(s) from CSA Group, please visit the store csagroup.org or call 1-800-463-6727.